



## Design and Fabrication of an Optimised Coal-Fired Crucible Pit Furnace

Akor, T., Jafaru A. M., Garuba, D. K.  
Mechanical Engineering Department,  
Nigerian Defence Academy Kaduna, Nigeria

### ABSTRACT

The main aim of this work was to upgrade the hole on the ground type of crucible furnace at the department of mechanical engineering workshop of the Nigerian Defence Academy into a more efficient and portable furnace that can be deployed even in a lecture room for heat treatment and other experimental work. This paper presents the design, construction procedures and result of the test for evaluating the performance of the optimized coal-fired crucible pit furnace. The shell is made of a mild-steel sheet of 2mm thickness, lined internally with refractory bricks. A motorized blower is incorporated to provide sufficient air circulation and pressure for effective combustion of the coal. Thermocouples and a pressure gauge are also attached to the shell to monitor the internal conditions of the furnace. The top of the furnace is closed with a brick walled cover fitted with a pipe to avoid convectional and radiation losses but allow for easy escape of combustion gasses. The crucible furnace was tested. It melted 2kg of aluminum- scrap in 18 minutes at a temperature of about 662°C. The furnace temperature was allowed to reach 782°C for the charge to completely melt and be fluid enough for casting. The thermal efficiency of the furnace is 14.7%; indicating very good performance. Normally the thermal efficiency for pit furnace is between 4-19%.

### ARTICLE INFO

#### Article History

Received: December, 2021

Received in revised form: February, 2022

Accepted: March, 2023

Published online: March, 2023

### KEYWORDS

Crucible furnace, Aluminum, Melting rate, Efficiency, furnace, refractory bricks

### INTRODUCTION

Nonferrous metals have been melted in crucibles for thousands of years. These crucibles are placed in a furnace and heated by available fuel. As the charge melts and attains the required pouring temperature, crucible is brought out of furnace with help of tongs. Crucible furnaces are generally employed in melting nonferrous metal. They are pit furnace, pot furnace, oil, coal, or charcoal fired furnace etc. Average capacity of these furnaces lies

between 30 to 150 kgs [1]. At the rural level, the foundry-man digs a hole on the ground to take the shape of an oven, which he fires using coal or charcoal as fuel. He makes use of either clay or metal pot as the crucible. A bellows or wheel blower system is employed to supply the air needed for the combustion process to provide the required heat for the melting of the metallic material being worked on. However, there are problems associated with working with this type of crucible

Corresponding author: Akor, T.

✉ [takor@nda.edu.ng](mailto:takor@nda.edu.ng)

Mechanical Engineering Department, Nigerian Defence Academy, Kaduna.

© 2023. Faculty of Tech. Education, ATBU Bauchi. All rights reserved



furnace. These include excessive fuel requirement, heat radiation on the operator; excessive heat loss in the system and excessive fuel consumption. The operation of the pit on the ground type of furnace is also time-consuming. This is because the air speed from the billows is too low to lit the charcoal efficiently [2, 3].

Progress has been made in the design of melting furnaces, from the wheel and fan system for non-ferrous materials like aluminum to the present day compact systems operated by electricity and those fired by solid, liquid and gaseous fuels which are capable of processing iron and steel; the major types of furnaces being; the induction furnaces, cupolas etc. These are expensive and out of reach of many who would want to venture into small scale foundry business. Attempts have been made by researchers in the production of low cost versions. Oyawale and Olawale, [4] designed and constructed a Mini-Electric Arc Furnace to melt 5kg of steel/cast iron scraps, using locally produced Soderberg electrodes. Tests carried out on the furnace showed that it required 60 minutes to heat up the furnace to the melting temperature of cast iron (1150°C - 1400°C). Furthermore, it took about 95 minutes to melt the first charge of 2kg resulting in a melting rate of 21.05g/minute. Alaneme et al [5] designed and constructed a diesel-fired furnace. An evaluation test on this furnace indicated that, it had a fast heating rate of about 61.24°C/min. with good heat retaining capacity and can be easily maintained. In Nigeria, the cost of liquid fuel and gas has become prohibitively high unlike solid fuel like coal which is glossily underutilized if

not abandoned.. At the current estimates, Nigeria's coal reserves amount to approximately 640 million proven tonnes and 2.75 billion tonnes of contingent reserves Chukwu et al. [5]. Coal is a biogenic sedimentary rock derived from complex biochemical and metamorphic processes termed coalification in the earth's crust Gra'bner [6]. In the context of energy recovery, coal is a brown-to-black combustible material that contains high carbon content (60wt%- 87wt %) Reddy [7] and higher heating values (14-34 MJ/kg). Speight [8]. Consequently, coal is predominantly utilised for electric power generation due to its high energy content, widespread availability, and low processing costs Dorf [5].

The discovery of new coal deposits in Nigeria presents numerous opportunities not only for the power and energy sectors Ohimain [5] but for socioeconomic growth, infrastructural and industrial development. This research aims to design and produce a crucible furnace that will utilize coal that is not only in abundance in Nigeria but is being underutilized. Because all the materials for the production of the crucible furnace with coal as its fuel which are locally available, it envisaged that this product will be very affordable and accessible by our local foundry men.

## MATERIALS AND METHODS

### Materials

The following materials were utilized in this study.

- (i) Coal which is generally classified based on its volatile matter [5]. Other materials include, low carbon steel sheet, refractory fire bricks and clay.

---

Corresponding author: Akor, T.

✉ [takor@nda.edu.ng](mailto:takor@nda.edu.ng)

Mechanical Engineering Department, Nigerian Defence Academy, Kaduna.

© 2023. Faculty of Tech. Education, ATBU Bauchi. All rights reserved



## Methods

The crucible pit furnace was constructed by using locally available materials. The pit furnace constructed is a bale out type designed to be portable. Plate 1 shows the design specifications of the crucible pit furnace in autographic projection. The specification for the furnace's shell and door cover is shown in Plate 2. Locally sourced clay and fire bricks were used for construction.

## Fabrication Procedure

### Marking out and cutting

This is the first stage in the fabrication of the crucible furnace which involved the marking out and cutting out of the required dimension of 562mm by 545mm from the 2mm mild steel sheet for the furnace casing. On to this sheet metal a 32mm diameter hole was made for the inlet of the blower. Another cutting made on this plate was a 160mm by 276mm gate made to be 41mm from the base, to provide for a gate for feeding the coal. A circular sheet plate of 545mm diameter was also cut out for the construction of the furnace base. Another circular plate of 266mm diameter was cut out for the furnace cover.

### Rolling and Welding

This process was employed to produce the casing for the furnace. The cut out sheet was rolled and welded into a cylindrical housing for the furnace frame of diameter 545mm and height 562mm.

### Refractory lining

Clay (sodium silicate) mixed with water, was used to set in place the 60mm thick fire bricks used for the

lining of the furnace wall and floor. The floor which is the base of the furnace was formed by first lining the base sheet metal with a thin layer of the clay (about 10mm thick). This was followed by laying the fire bricks on the clay lining and allowed to set. The welded shell was then set in place and the inner wall was plastered with a thin layer of the clay also about 10mm thick. The 60mm thick fire bricks were then used to line the inner wall of the shell by joining them together using the clay. After setting, another 26mm layer of clay, was applied to smoothen the inner wall of the furnace giving a final wall thickness of 96mm leaving a furnace internal diameter of 449mm. The furnace body was then allowed to dry for 21 days for proper curing and any cracks noticed were repaired.

### Furnace Cover and Stand

The fabrication of the cover was based on the internal diameter of the furnace. A cover of diameter 520mm and rim height of 80mm was made from the sheet metal and was lined with clay and fire bricks as was done for the floor and shell. A hole was provided at the center of the cover and a steel pipe welded on top to act as vent for the furnace. Galvanized steel pipes of 25mm diameter by 305mm were cut and welded to the base of the shell and brazed to provide the stand for the furnace.

### The blower assembly

The blower of variable speed was bought off shelf. It was coupled to a steel pipe, 25mm in diameter by 440mm attached with a control valve which was used to link the blower and the burner

---

Corresponding author: Akor, T.

✉ [takor@nda.edu.ng](mailto:takor@nda.edu.ng)

Mechanical Engineering Department, Nigerian Defence Academy, Kaduna.

© 2023. Faculty of Tech. Education, ATBU Bauchi. All rights reserved

for the supply of air required for combustion. The blower was attached

on a metallic stand constructed as its sitting.

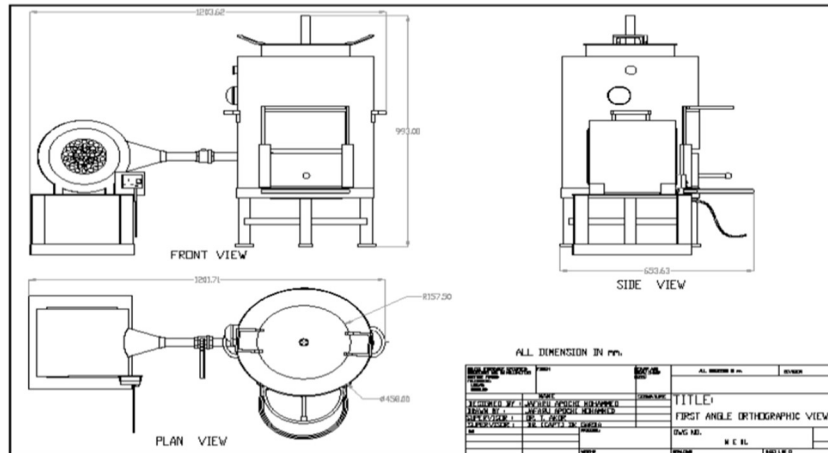


Plate1: Projections of the three views of the furnace (first angle projection)

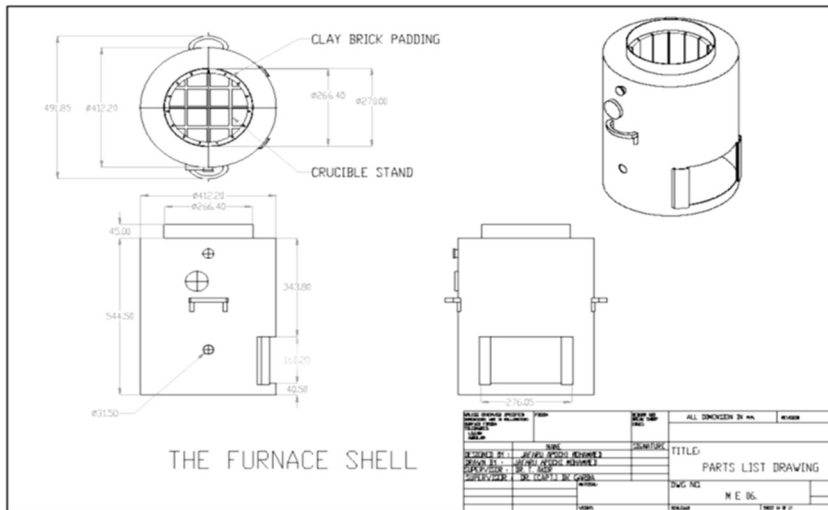


Plate 2: Specification for the furnace's shell and door.

### Assembly

The different components of the furnace produced as shown in plates 3a-f were assembled together starting with the burner, then the blower and the

furnace cover as in Plate 4. After that temperature and pressure gauges were installed for monitoring the conditions in the furnace during firing.

Corresponding author: Akor, T.

✉ [takor@nda.edu.ng](mailto:takor@nda.edu.ng)

Mechanical Engineering Department, Nigerian Defence Academy, Kaduna.

© 2023. Faculty of Tech. Education, ATBU Bauchi. All rights reserved



**Plate 3a** Furnace cover



**Plate 3b:** Blower assembly



**Plate 3c:** Coupling from blower to burner.



**Plate 3d:** Burner assembly



**Plate 3e:** Cover for the fuel port.



**Plate 3f:** Furnace shell

---

Corresponding author: Akor, T.

✉ [takor@nda.edu.ng](mailto:takor@nda.edu.ng)

Mechanical Engineering Department, Nigerian Defence Academy, Kaduna.

© 2023. Faculty of Tech. Education, ATBU Bauchi. All rights reserved



Plate 4a & 4b: The produced crucible furnace before and after painting

### *Performance Evaluation*

Some quantity of coal; 3kg was added into the fuel tray and kindled from outside the furnace and allowed to burn for about ten minutes. The fuel tray was then slid into the heating chamber. Thereafter the crucible was placed on top of its stand above fuel tray in the heating chamber. The furnace was then covered with the lid. The blower system was connected to the fuel tray within the heating chamber. The temperature gauge was then screwed into the thermocouple drum which protruded into the combustion chamber

to monitor temperature change within the chamber. The control valve for the blower was gradually set until the required air pressure for adequate combustion in the heating chamber was attained. The heating of the crucible with the 2kg aluminum was timed and temperature readings were taken at time intervals of 3min. The furnace was fired until it attained the temperature of 782°C. It took 18 minutes to completely melt the aluminum charge to its pouring temperature. Giving a melting rate of 111g/min.



Plate 5: Melting of 5kg aluminum -scrap



Plate 6: Baring the crucible with the melt

Corresponding author: Akor, T.

✉ [takor@nda.edu.ng](mailto:takor@nda.edu.ng)


Mechanical Engineering Department, Nigerian Defence Academy, Kaduna.

© 2023. Faculty of Tech. Education, ATBU Bauchi. All rights reserved

## RESULT AND DISCUSSION

**Table 1:** Heating Rate of the 2kg aluminum-scrap ( $^{\circ}\text{C}/\text{min}$ )

Time (min)	Temperature Attained ( $^{\circ}\text{C}$ )	Heating Rate ( $^{\circ}\text{C}/\text{min}$ )
3	128	42.00
6	271	45.00
9	400	44.00
12	519	43.00
15	661	44.10
18	782	43.00
21	913	43.50
24	1072	44.67
27	1225	45.40
30	1330	44.33
33	1388	42.01
Average Heating Rate	43.73	

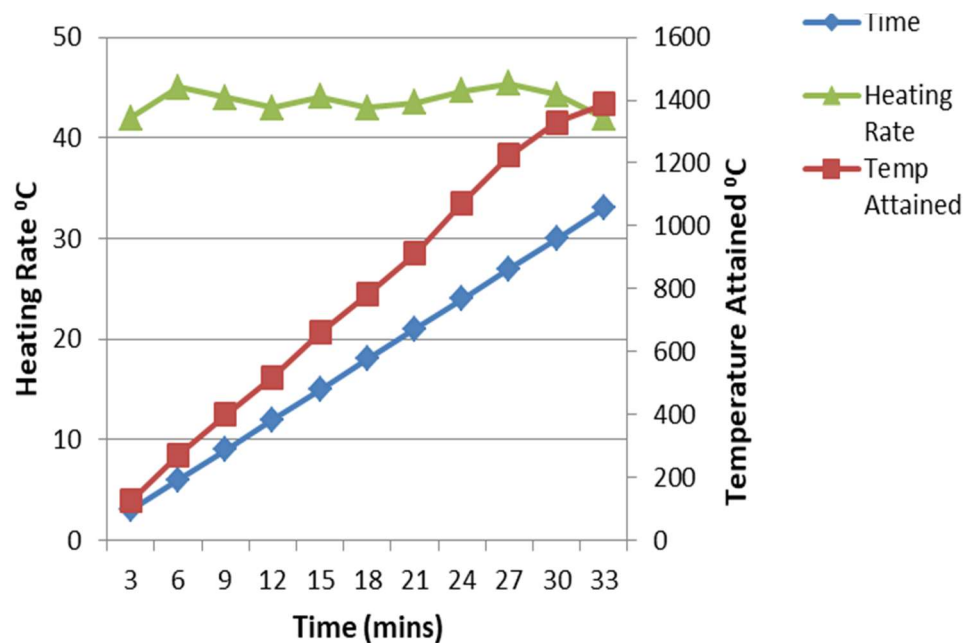

**Figure 1:** Graph of Heating Rate and Temperature Attained with Time

The efficiency of the furnace was calculated by direct method considering the amount of heat required to melt the scarp to the amount of fuel energy to melt the scarp. In other words,

It was determined by measuring the amount heat absorbed by the stock and dividing this by the total amount of fuel consumed' Furnace's efficiency is increased when the percentage of heat

Corresponding author: Akor, T.

✉ [takor@nda.edu.ng](mailto:takor@nda.edu.ng)

Mechanical Engineering Department, Nigerian Defence Academy, Kaduna.

© 2023. Faculty of Tech. Education, ATBU Bauchi. All rights reserved

that is transferred to the stock or load inside the furnace increases.

$$\text{Therefore, } \text{Thel.} = \frac{\text{total heat required to melt the charge (aluminum)} Q_s}{\text{total heat supplied by the fuel (coal)} Q_f}$$

Where;

Thel = Thermal efficiency of furnace (%)

$Q_s$  = the total amount of heat required to melt the aluminum (KJ)

$Q_f$  = the amount of heat supplied by the fuel to melt the charge (KJ)

The total heat required melt the charge  $Q_s$  is given by:

$$Q_s = M \times C_p \times (\Delta T) \text{ -----Equ. 1}$$

Where;

$M$  = mass of metal (kg)

$C_p$  = specific heat capacity of aluminum (KJ/kg K)

$\Delta T$  = temperature difference ( $T_a - T_f$ ) ( $^{\circ}\text{C}$ )

$T_a$  = ambient temperature

$T_f$  = maximum furnace temperature

The total heat supplied by the fuel is given  $Q_f$

$$Q_f = L_f \times S_g \times T_t \times C_v \text{ -----Equ 2}$$

Where;

$Q_f$  = amount of heat supplied (KJ)

$L_f$  = Quantity of fuel consumed (liters)

$S_g$  = Specific gravity of fuel

$T_t$  = Time taken to melt the stock

$C_v$  = Calorific value of fuel (KJ) Kg K)

According to ASTM standards coal has a calorific value of 8000KJ/kg and specific gravity of 1.3. The specific heat capacity of aluminum scrap is 0.920KJ/kgK [8, 9]

From equation 1,

$$\text{The heat required to melt the aluminum } Q_s = 2 \times 0.920 \times (782-32^{\circ}\text{C}) \\ (32^{\circ}\text{C was the ambient temperature)} = \mathbf{1380 \text{ KJ.}}$$

From equation 2.

$$\text{The heat supplied by the fuel, heat input } Q_f = 3 \times 1.3 \times 0.3 \times 8000 \\ = \mathbf{9360 \text{ KJ}}$$

$$\text{The thermal efficiency of the furnace } Q_s/Q_f = \frac{1380\text{KJ}}{9360\text{KJ}} \times 100 = \mathbf{14.7\%}$$

## CONCLUSION

The developed furnace is a great improvement on the pit on the ground, bellow utilizing type of furnace. The optimized furnace efficiency of 14.7%; compares well with other works. The crucible pit furnace designed by Bhandari S.S. et al that uses coal as fuel yielded an efficiency of 13.72%.

Normally pit furnace efficiency lies between 4% - 19%. The furnace may be effectively used for melting non-ferrous metals for casting and other experimental works by students. It is also a value addition for coal which is grossly underutilized.

Corresponding author: Akor, T.

✉ [takor@nda.edu.ng](mailto:takor@nda.edu.ng)

Mechanical Engineering Department, Nigerian Defence Academy, Kaduna.

© 2023. Faculty of Tech. Education, ATBU Bauchi. All rights reserved





## REFERENCES

- 1 Gupta J. (2008); "Elements of Fuels, Furnaces and Refractory's", 5th Edition, Romesh Chanda Khanna, New Delhi, pp.1089- 1458
- 2 Osarenmwinda, J. O. (2015); "Fabrication and Performance Evaluation of Oil-Fired Crucible Furnace Using Locally Sourced Materials". International Journal of Engineering Research and Applications, 5(3); 29-33.
- 3 Abasiryu, T., Ayuba, A., and Zira, A. E. (2016); "Performance evaluation of some locally fabricated cookstoves in Mubi, Adamawa state, Nigeria". Nigerian Journal of Technology, 35(1), 48-53.
- 4 Venkanna, B. K. (2010); "Fundamentals of heat and mass transfer". PHI Learning Pvt. Ltd.
- 5 Okafor, B. E. (2016); "Development of Coal Fired Furnace for Small Scale ". ISSN: 2049-3444 © 2016 - IJET Publications UK. All rights reserved.
- 6 Chukwudi, B.C. and M.B. Ogunedo. 2017; "Design and Development of a Gas Fired Reverberatory Furnace: In View of Huge Gas Reserves in Nigeria". Pacific Journal of Science and Technology. 8(1):13-21.
- 7 Alaneme K. K. and Olanrewaju S. O. (2010): "Design of a Diesel Fired Heat-Treatment Furnace", Journal of Minerals and Materials Characterization and Engineering. Vol. 9, no.7, pp. 581-591.
- 8 R. Suresh, M. G Nagarjun. (2016). Construction and performance analysis of pit furnace by using bio- disel. Indian journal of science and technology. 9(45), 1-5 available at: <file:///C:/users/DST/Downloads/104587-234986-1-PB.pdf>
9. Kothandaraman CP & Subramanyan S. (2014). Heat transfer data hand book. (8<sup>th</sup> edition). Ned Delhi, India: New age international (P) limited. Available at <https://www.abebooks.co.uk/book-search/title/heat-and-mass-transfer-data-book/author/kothandaraman-c-p-and-subramanyan-s/>

---

Corresponding author: Akor, T.

✉ [takor@nda.edu.ng](mailto:takor@nda.edu.ng)

Mechanical Engineering Department, Nigerian Defence Academy, Kaduna.

© 2023. Faculty of Tech. Education, ATBU Bauchi. All rights reserved